

DC53

High Hardness & Toughness
New General-Purpose Cold Die Steel

Features

- 1 Higher hardness after heat treatment than SKD11**
A Hardness of HRC 62-63 is secured after tempering at high temperatures (520-530°C). Therefore, DC53 exceeds SKD11 in strength and wear resistance.
- 2 Double the toughness of SKD11**
DC53 has relatively well-performing toughness among all cold die steels. Therefore, tools and dies made of DC53 are less faced with the problems such as cracking and chipping, which often seriously affect conventional tools and dies, and enjoy greater durability.
- 3 Less residual stress after wire electro-discharge machining**
Residual stress is lessened by means of high-temperature tempering. Therefore, problems such as cracking and distortion are prevented during and after wire electro-discharge machining.
- 4 Excellent machinability and grindability**
DC53 is superior to SKD11 in machinability and grindability. Therefore, the use of DC53 is expected to provide relatively longer tool life and reduces the number of processes in die making.

Applications

- 1 Precision press dies**
Wire discharge processed press dies for fine blanking, composite processing, etc.
- 2 Plastic forming tools for hard-to-work materials**
Dies for cold forging, deep drawing, and thread rolling
- 3 Other**
High-speed blanking punches, stainless steel sheet punches




DAIDO STEEL

Heat Treatment




Our newly developed cold die steel, DC53, is an improvement over the alloy tool steel SKD11 specified in Japanese Industrial Standard (JIS) G4404. It eliminates the disadvantage of insufficient hardness and toughness, resulting from high-temperature tempering found with SKD11, and is intended to replace SKD11 in use for general purposes and precision dies.

● Quenching hardness curve

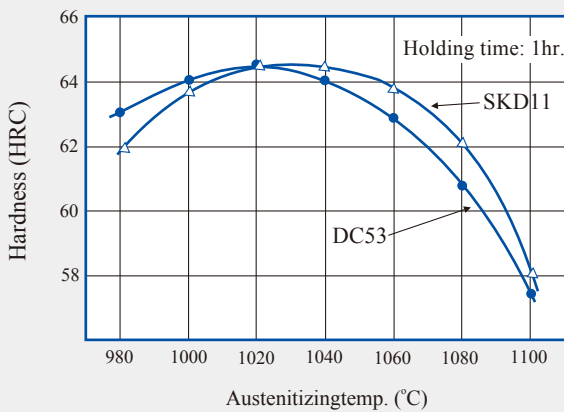


● Quenching & tempering hardness curve

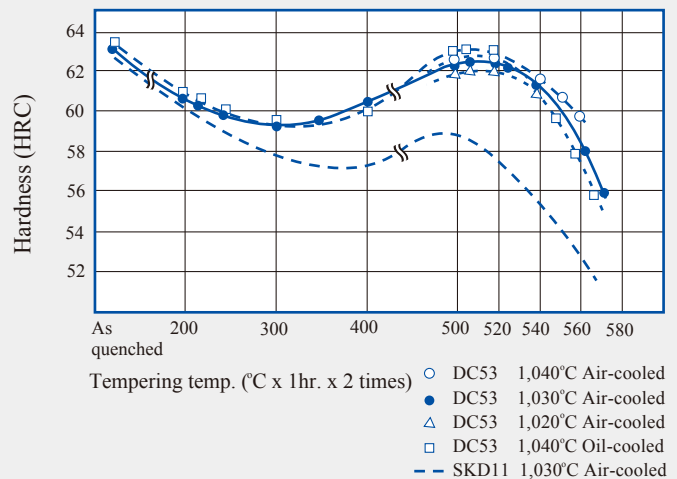

[Standard Heat Treatment Conditions]

● Usual quenching

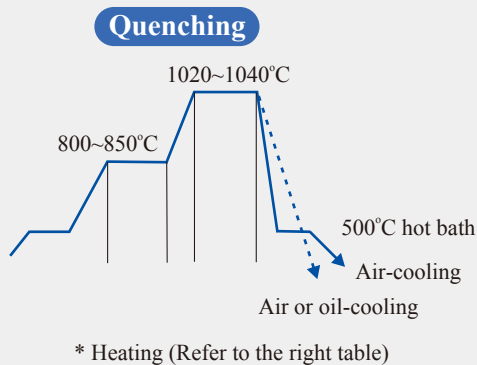


Standard heating time (salt bath)


Dia. thickness (mm)	Immersing time (min)
5	5-8
10	8-10
20	10-15
30	15-20
50	20-25
100	30-40

Tempering

- Low-Temperature: 180~200°C
- High-Temperature: 500~550°C

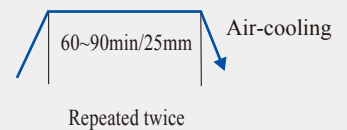

● Vacuum quenching

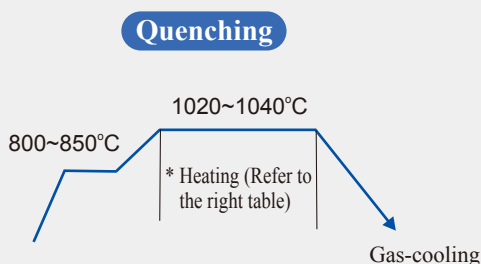


Standard heating time

Thickness (mm)	Heating time
100mm and under	20-30min/25mm
Over 100mm	10-20min/25mm

Tempering


- Low-Temperature: 180~200°C
- High-Temperature: 500~550°C

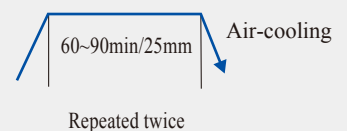


Quality Characteristics




● Relationship Between Tempering Temperature and Impact Value

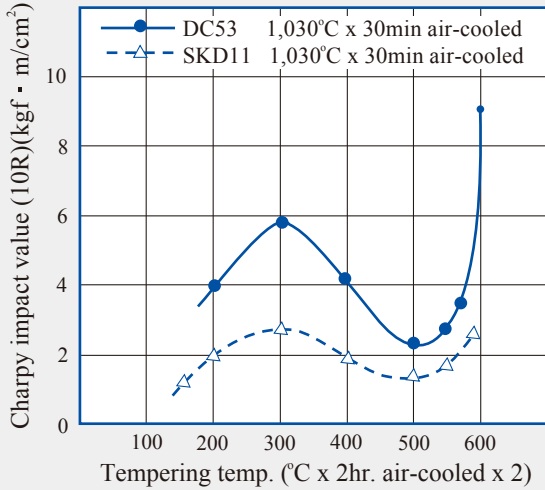


● Relationship Between Hardness and Impact Value

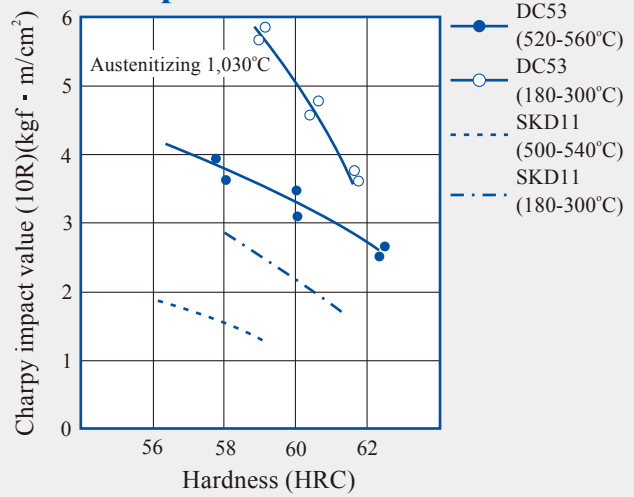


● Abrasion Test (Ohgoshi Method)

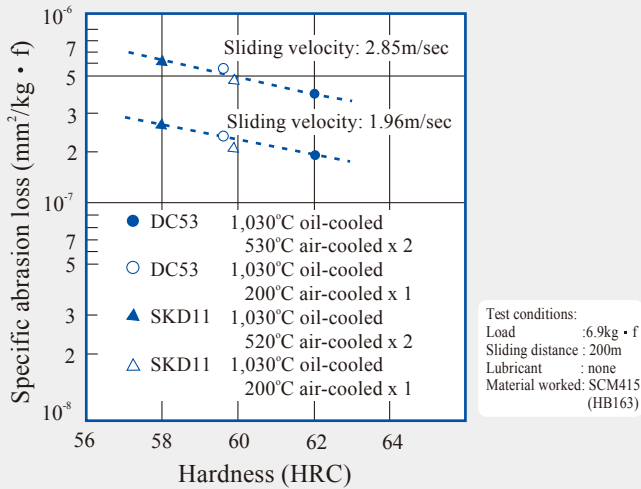


● Durability of Drilling Tool

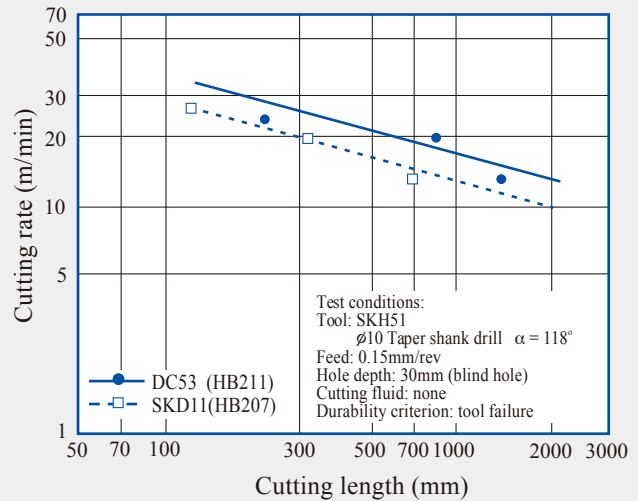

● Dimensional Changes due to Heat Treatment

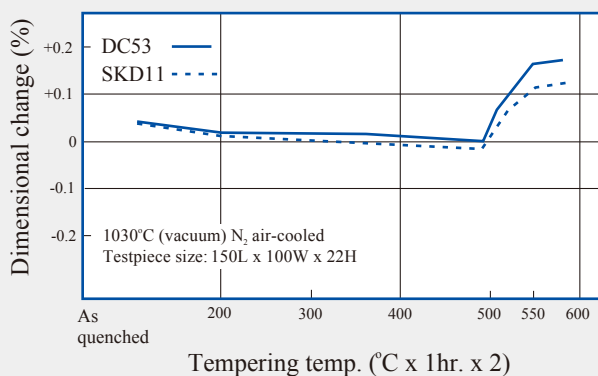

● Relationship Between Tempering Temperature and amount of Retained Austenite

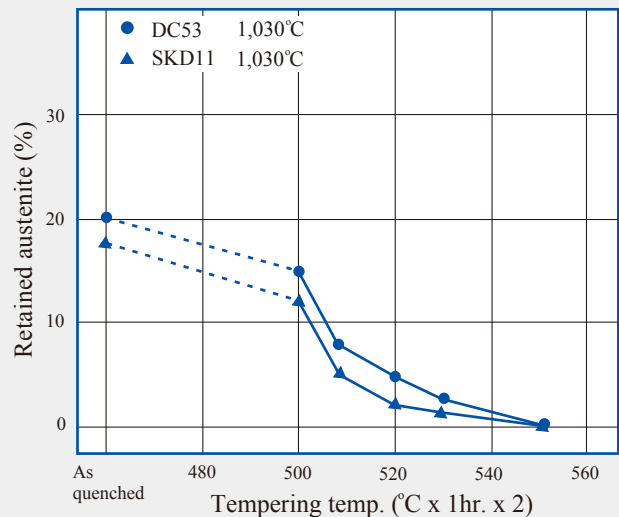

● Physical Properties

Specific gravity (g / cm ³)	7.87					
Coefficient of expansion (x 10 ⁻⁶ / °C)	-150°C	-200°C	-300°C	Retained austenite 14%		
	13.0	13.5	14.2			
Thermal conductivity (cal / cm · sec · °C)	Room temperature	100°C	200°C	300°C	400°C	500°C
	0.057	0.060	0.064	0.064	0.065	0.062
Young's modulus (E)	21,700 (kgf / mm ²)					
Modulus of rigidity (G)	8,480 (kgf / mm ²)					
Poisson's ration (ν)	0.28					

● Stabilization Treatment

It is possible to control dimensional change with time by additional stabilization treatment (250°C~400°C) after high-temperature tempering.

The best temperature of stabilization treatment is 400°C.

● Heat Treatment vs. Properties

	Heat Treatment	Dimensional change with time	Dimensional change in HT	Dimensional change in W-EDM	Hardness (HRC)	Toughness
1	H : 1030°C T : 180 - 200°C TWICE	◎	Small	△	60-61	◎
2	H : 1030°C T : 500°C TWICE	△	Small	○	60-61	○
3	H : 1030°C T : 500 - 540°C TWICE	△	Large	◎	61-63	◎
4	H : 1030°C T : 500 - 540°C TWICE + 400°C	◎	Large	◎	60-63	◎



Tokyo Head Office
(Export Sales Dept.)
Daido Steel(America)Inc.

Daido Shinagawa Building, 6-35, 1-Chome, Konan, Minato-ku, Tokyo, Japan
Phone:+81-3-5495-1270 Fax:+81-3-5495-6738
1111 Plaza Drive, Suite 740, Schaumburg, IL 60173, U.S.A.
Phone:+1-847-517-7950 Fax:+1-847-517-7951

Bangkok Office

120 Moo 5, Wellgrow Industrial Estate, Bangna-Trad Road, KM.36, Bangsamak, Bangpakong, Chachoengsao 24180, Thailand
Phone:+66-38-571317 Fax:+66-38-571313

Daido Steel (Shanghai) Co.,Ltd.

Room 1402, Ruijin Building, 205 Mao Ming Nan Road, Shanghai 200020, China
Phone:+86-21-5466-2020 Fax:+86-21-5466-0279

Daido Steel (Shanghai) Co.,Ltd.
Guangzhou Subsidiary Company

Room 2601, No.8, Linhezong Road, Tianhe District, Guangzhou 510610, China
Phone:+86-20-3877-1632 Fax:+86-20-8550-1126

Document Disclaimer

The product characteristics included in this brochure are the representative values based on the result of our measurements, and do not guarantee the performance in use of the products. Please inquire the latest information to our department in charge as the information of this brochure is updated without previous notice as needed.

Copyright © 1984 Daido Steel Co., Ltd. All rights reserved.